

ISSN 1410-9530 (Print)
ISSN 1979-570X (Online)

CIVIL ENGINEERING DIMENSION

Journal of Civil Engineering Science and Application

Dimensi Teknik Sipil
Jurnal Keilmuan dan Penerapan Teknik Sipil

Editors

Prof. Dr. Benjamin Lumantarna

(Petra Christian University, Surabaya, INDONESIA, SCOPUS ID = 54179537600)

Prof. Dr. Djwantoro Hardjito

(Petra Christian University, Surabaya, INDONESIA, SCOPUS ID = 6508089898)

Dr. Benny Suryanto

(Heriot-Watt University, Edinburgh, UNITED KINGDOM, SCOPUS ID = 36618184800)

Board of International Reviewers

Prof. Dr. David Arditi

(Illinois Institute of Technology, Illinois, USA, SCOPUS ID = 35614735000)

Prof. Dr. Stephen Olu Ogundana

(Heriot-Watt University, Edinburgh, UNITED KINGDOM, SCOPUS ID = 6701638480)

Prof. Dr. Priyan Mendis

(University of Melbourne, Melbourne, AUSTRALIA, SCOPUS ID = 7003700296)

Prof. Dr. Worsak Kanok-Nukulchai

(Asian Institute of Technology, Bangkok, THAILAND, SCOPUS ID = 7004839869)

Dr. Robby Soetanto

(Loughborough University, Loughborough, UNITED KINGDOM, SCOPUS ID = 8870442200)

Prof. Dr. Iswandi Imran

(Bandung Institute of Technology, Bandung, INDONESIA, SCOPUS ID = 6603209142)

Prof. Dr. Jeff Budiman

(Illinois Institute of Technology, Illinois, USA, SCOPUS ID = 6603239355)

Dr. Andreas

Nataatmadja, MIEAust, M. ASCE

(University of Southern Queensland, Toowoomba, AUSTRALIA, SCOPUS ID = 6602640350)

Dr. Riza Yosia Sunindijo

(University of New South Wales, Sydney, AUSTRALIA, SCOPUS ID = 21741351400)

Prof. Dr. Masyhur Irsyam

(Bandung Institute of Technology, Bandung, INDONESIA, SCOPUS ID = 6505844516)

Dr. Dradjat Hoedajanto

(Indonesian Society of Civil and Structural Engineers, INDONESIA)

Dr. Andi

(Petra Christian University, Surabaya, INDONESIA, SCOPUS ID = 7409720298)

Dr. Elisa Lumantarna

(University of Melbourne, Melbourne, AUSTRALIA, SCOPUS ID = 6504537022)

Dr. Kardi Teknomo

(Ateneo de Manila)

HOME ABOUT LOGIN REGISTER SEARCH CURRENT ARCHIVES
PUBLICATION ETHICS AND MALPRACTICE STATEMENT GUIDES FOR AUTHORS

Home > Vol 21, No 2 (2019)

Civil Engineering Dimension



Civil Engineering Dimension (CED) is a peer-reviewed journal supported by Petra Christian University.

The Civil Engineering Dimension (CED) was first accredited by the Directorate General of Higher Education of Indonesia in 2000, with its decree No. 395/DIKTI/Kep/2000. Since then, CED has been honored with the [accreditation](#) status without any interruption. The latest accreditation decree is No. 51/E/KPT/2017, dated 4 December 2017, valid for 5 (five) years. CED has been granted the status of green tick by DOAJ (<http://www.doaj.org>).

The Civil Engineering Dimension (Dimensi Teknik Sipil) is a refereed journal, published twice a year, in **March** and **September**.

[accreditation certificate](#)

Vol 21, No 2 (2019): SEPTEMBER 2019

Table of Contents

Articles

- [PEMS-on board and E3 Modeling: A Comparison between Real-World Measurement and Emissions Estimates from Construction Equipment](#) [PDF](#) 59-65
Apif M. Hajji M. Hajji, Aisyah Larasati, Michael P. Lewis, Huang Yue
- [Analysis of Different Stripe Connectors for a Gabion Wall based on Woven Waste Tire Stripes](#) [PDF](#) 66-69
Arwan Apriyono, Sumiyanto Sumiyanto, Yanto Yanto, Sachrul Iswahyudi, Rino Wahyu Pamungkas
- [Intensity-Duration-Frequency \(IDF\) Curve and the Most Suitable Method to Determine Flood Peak Discharge in Upper Werba Sub-Watershed](#) [PDF](#) 70-75
Cilcia Kusumastuti, Prasetyo Sudjarwo, Marvin Christhie, Timotius Krisna
- [Permeation Resistance of Sawdust Ash Blended Cement Laterized Concrete](#) [PDF](#) 76-83
Samuel Olufemi Folagbade, Aluko Olawale
- [Study on Graphite Powder as Conductive Pigments for Impressed Current Cathodic Protection System using Carbon Fiber Reinforced Polymer Anode](#) [PDF](#) 84-88
Gunawan Budi Wijaya, David Pratama Lays, Hongky Haodwidjaya Tanto, Daniel Tjandra
- [On the Derivation of Exact Solutions of a Tapered Cantilever Timoshenko Beam](#) [PDF](#) 89-96
Foek Tjong Wong, Junius Gunawan, Kevin Agusta, Herryanto Herryanto, Levin Sergio Tanaya
- [Seismic Vulnerability Maps of Ratu Agung District, Bengkulu City, Indonesia](#) [PDF](#) 97-106
Lindung Zalbuin Mase
- [Effect of Crumb Rubber as Fine Aggregate Replacement in Cold Mixture Asphalt](#) [PDF](#) 107-112
Paravita Sri Wulandari, Ken Kertorahardjo, Arianto Thesman, Daniel Tjandra

CED is published by The Institute of Research & Community Outreach - Petra Christian University, Surabaya, Indonesia



©All right reserved 2016. *Civil Engineering Dimension*, ISSN: 1410-9530, e-ISSN: 1979-570X

[00190379](#) [View My Stats](#)

Accredited by the Ministry of Research, Technology, and Higher Education, Indonesia

- Vol 2 - Vol 4 : No. 395/DIKTI/Kep/2000
- Vol 5 - Vol 7 : No. 49/DIKTI/Kep/2003
- Vol 8 - Vol 10 : No. 55a/DIKTI/Kep/2006
- Vol 11 - Vol 13 : No. 110/DIKTI/Kep/2009
- Vol 14 - Vol 19 : No. 80/DIKTI/Kep/2012
- Vol 20 : No. 51/E/KPT/2017

USER

Username
Password
☐ Remember me
[Login](#)

[Journal Help](#)

JOURNAL CONTENT

Search
Search Scope
All
[Search](#)

Browse
• [By Issue](#)
• [By Author](#)
• [By Title](#)
• [Other Journals](#)

INFORMATION

- [For Readers](#)
- [For Authors](#)
- [For Librarians](#)

FONT SIZE

NOTIFICATIONS

- [View](#)
- [Subscribe](#)

CURRENT ISSUE

ATOM 1.0
AS2 2.0
AS2 1.0



Abstracting and Indexing - Jurnal Civil Engineering Dimension

Google Scholar

DOAJ DIRECTORY OF OPEN ACCESS JOURNALS

EBSCO HOST

crossref

University, Quezon City,
PHILIPPINES, SCOPUS ID
= 14012002200)

Dr. Antoni

(Petra Christian
University, Surabaya,
INDONESIA, SCOPUS ID
= 12796152500)

Dr. Hartanto Wibowo

(Iowa State University,
Ames, USA, SCOPUS ID =
35249850200)

Dr. Dario Rosidi

(CH2M HILL Corporation,
Oakland, USA, United
States, SCOPUS ID =
6506775115)

**Dr. Muslinang
Moestopo**

(Indonesian Society of
Civil and Structural
Engineers, INDONESIA,
SCOPUS ID =
36696777500)

**Ir. Johannes I.
Suwono, M.Eng.**

(Geotechnical
Engineering, Civil
Engineering, Department, Petra
Christian University,
INDONESIA)

Dr. Gogot Setyo Budi

(Petra Christian
University, Surabaya,
INDONESIA, SCOPUS ID
= 57170817700)

**Dr.rer.nat. Surya
Hermawan**

(Petra Christian
University, Surabaya,
INDONESIA)

Administrative

Assistant:

Sumarno



**Editor and
Administration
Address:**

Institute of Research and
Community Outreach
Petra Christian University

Jl. Siwalankerto 121-131,
Surabaya 60236
Indonesia
Phone: +62-31-2983139,
2983147
Fax: +62-31-8436418,
8492562
E-mail:
dimensi-sipil@petra.ac.id

Homepage:
<http://ced.petra.ac.id>

CIVIL ENGINEERING DIMENSION

Journal of Civil Engineering Science and Application

Dimensi Teknik Sipil
Jurnal Keilmuan dan Penerapan Teknik Sipil

Vol 21, No 2 (2019)

SEPTEMBER 2019

Table of Contents

Articles

PEMS-on board and E3 Modeling: A Comparison between Real-World Measurement and Emissions Estimates from Construction Equipment	PDF
Apif M. Hajji M. Hajji, Aisyah Larasati, Michael P. Lewis, Huang Yue	59-65
Analysis of Different Stripe Connectors for a Gabion Wall based on Woven Waste Tire Stripes	PDF
Arwan Apriyono, Sumiyanto Sumiyanto, Yanto Yanto, Sachrul Iswahyudi, Rino Wahyu Pamungkas	66-69
Intensity-Duration-Frequency (IDF) Curve and the Most Suitable Method to Determine Flood Peak Discharge in Upper Werba Sub-Watershed	PDF
Cilcia Kusumastuti, Prasetio Sudjarwo, Marvin Christhie, Timotius Krisna	70-75
Permeation Resistance of Sawdust Ash Blended Cement Laterized Concrete	PDF
Samuel Olufemi Folagbade, Aluko Olawale	76-83
Study on Graphite Powder as Conductive Pigments for Impressed Current Cathodic Protection System using Carbon Fiber Reinforced Polymer Anode	PDF
Gunawan Budi Wijaya, David Pratama Lays, Hongky Haodiwidjaya Tanto, Daniel Tjandra	84-88

[On the Derivation of Exact Solutions of a Tapered Cantilever Timoshenko Beam](#)

[PDF](#)

Foek Tjong Wong, Junius Gunawan, Kevin Agusta, Herryanto Herryanto, Levin Sergio Tanaya 89-96

[Seismic Vulnerability Maps of Ratu Agung District, Bengkulu City, Indonesia](#) [PDF](#)

Lindung Zalbuin Mase

97-106

[Effect of Crumb Rubber as Fine Aggregate Replacement in Cold Mixture Asphalt](#) [PDF](#)

Paravita Sri Wulandari, Ken Kertorahardjo, Arianto Thesman, Daniel Tjandra 107-112

CED is published by The Institute of Research & Community Outreach - Petra Christian University, Surabaya, Indonesia



©All right reserved 2016. *Civil Engineering Dimension*, ISSN: 1410-9530, e-ISSN: 1979-570X

Home / Editorial Team

Editorial Team

Editor in Chief

Prof. Dr. Djwantoro Hardjito

(Petra Christian University, Surabaya, INDONESIA, SCOPUS ID = 6508089898)

Associate (Handling) Editors

Prof. Dr. Benjamin Lumantarna

(Petra Christian University, Surabaya, INDONESIA, SCOPUS ID = 54179537600)

Dr. Doddy Prayogo

(Petra Christian University, Surabaya, INDONESIA, SCOPUS ID = 55959834900)

Advisory International Editorial Boards

Prof. Dr. David Arditi

(Illinois Institute of Technology, Illinois, USA, SCOPUS ID = 35614735000)

Prof. Dr. Stephen Olu Ogunlana

(Heriot-Watt University, Edinburgh, UNITED KINGDOM, SCOPUS ID = 6701638480)

Prof. Dr. Priyan Mendis

(University of Melbourne, Melbourne, AUSTRALIA, SCOPUS ID = 7003700296)

Prof. Dr. Hu, Hsuan Teh

(National Cheng Kung University, Tainan, TAIWAN, SCOPUS ID = 55805441800)

Prof. Dr. Henk Marius Jonkers

(Delft University of Technology, Delft, NETHERLAND, SCOPUS ID = 7004676830)

Prof. Dr. Buntara S. Gan

(Nihon University, Tokyo, JAPAN, SCOPUS ID = 53864786800)

Prof. Dr. Worsak Kanok-Nukulchai

(Asian Institute of Technology, Bangkok, THAILAND, SCOPUS ID = 7004839869)

Prof. Dr. Jeff Budiman

(Illinois Institute of Technology, Illinois, USA, SCOPUS ID = 6603239355)

Prof. Dr. Iswandi Imran

(Bandung Institute of Technology, Bandung, INDONESIA, SCOPUS ID = 6603209142)

Prof. Dr. Masyhur Irsyam

(Bandung Institute of Technology, Bandung, INDONESIA, SCOPUS ID = 6505844516)

A/Prof. Dr. Riza Yosia Sunindijo

(University of New South Wales, Sydney, AUSTRALIA, SCOPUS ID = 21741351400)

A/Prof. Dr. Benny Suryanto

(Heriot-Watt University, Edinburg, UNITED KINGDOM, SCOPUS ID = 36618184800)

Focus and Scope

Peer Reviewers

Author Guidelines

Peer Review Process

Publication Ethics

Author Fees

Open Access

Plagiarism Check

CED Indexing & Abstracting





Crossref

DOAJ



MENDELEY

Editor and Administration Address:

Institute of Research and Community Outreach
Petra Christian University

Jl. Siwalankerto 121-131, Surabaya 60236

Indonesia

Phone: +62-31-2983139, 2983147

Fax: +62-31-8436418, 8492562

E-mail:

dimensi-sipil@petra.ac.id

Homepage:

<http://ced.petra.ac.id>

Accredited by the Directorate General of Higher Education, Indonesia

Vol 2 - Vol 4 : No. 395/DIKTI/Kep/2000

Vol 5 - Vol 7 : No. 49/DIKTI/Kep/2003

Vol 8 - Vol 10 : No. 55a/DIKTI/Kep/2006

Vol 11 - Vol 13 : No. 110/DIKTI/Kep/2009

Vol 14 - Vol 19 : No. 80/DIKTI/Kep/2012

Vol 20 : No. 51/E/KPT/2017

00274578 [View My Stats](#)

CED is published by The Institute of Research & Community Outreach - Petra Christian University, Surabaya, Indonesia

©All right reserved 2021. *Civil Engineering Dimension*, ISSN: 1410-9530, e-ISSN: 1979-570X

Platform &
workflow by
OJS / PKP



KEMENTERIAN RISET, TEKNOLOGI, DAN PENDIDIKAN TINGGI
DIREKTORAT JENDERAL PENGUATAN RISET DAN PENGEMBANGAN
DIREKTORAT PENGELOLAAN KEKAYAAN INTELEKTUAL

Sertifikat

Kutipan dari Keputusan Direktur Jenderal Penguatan Riset dan Pengembangan Kementerian Riset, Teknologi, dan Pendidikan Tinggi Republik Indonesia
Nomor: 51/E/KPT/2017, Tanggal 4 Desember 2017
Tentang Hasil Akreditasi Terbitan Berkala Ilmiah Elektronik
Periode II Tahun 2017

Nama Terbitan Berkala Ilmiah
Civil Engineering Dimension
ISSN: 1979-570X
Penerbit: Universitas Kristen Petra

Ditetapkan sebagai Terbitan Berkala Ilmiah

TERAKREDITASI

Akreditasi sebagaimana tersebut di atas berlaku selama
5 (lima) tahun sejak ditetapkan.

Jakarta, 5 Desember 2017
Direktur Pengelolaan Kekayaan Intelektual,

Dr. Sadjuga, M.Sc
NIP. 195901171986111001



Study on Graphite Powder as Conductive Pigments for Impressed Current Cathodic Protection System using Carbon Fiber Reinforced Polymer Anode

Wijaya, G.B.^{1*}, Lays, D.P.¹, Tanto, H.H.¹, Tjandra, D.¹

Abstract: The use of Carbon Fiber Reinforced Polymer (CFRP), for both strengthening material and anode for Impressed Current Cathodic Protection (ICCP) system, is being investigated. The focus of this study is to develop the epoxy that has good bond strength and electrical conductivity. Graphite powder is used as conductive pigments with percentage ranges from 7.5% to 17.5%. All specimens were partially submerged in 5% NaCl solution and induced with electrical current of 10 mA/m² and 20 mA/m² for 30 days. An average potential increase of 200 mV was recorded using half cell potential test. The application of 30 days ICCP up to current density of 20 mA/m² did not affect the bond strength significantly and still complies with ACI recommendation. However, graphite content of more than 15% are found to be not workable and the bond strength is greatly reduced to less than 1 MPa. This study concluded that the recommended graphite powder content shall be in the range of 10% to 15%.

Keywords: Carbon fiber reinforced polymer laminate; graphite powder; half cell potential; impressed current cathodic protection system; pull-off test.

Introduction

Reinforced concrete structure when exposed to aggressive environment tends to suffer from deterioration due to reinforcement corrosion. When not treated well, this will lead to strength loss and subsequently structural failure. Externally bonded Carbon Fiber Reinforced Polymer (CFRP) laminate has been used as an effective strengthening system. In this regard, Epoxy plays the most critical role to transfer the strain from the concrete substrate to the CFRP laminate.

US Federal Highway Administration (FHWA) stated that Cathodic Protection is the only rehabilitation technique that has been proven to stop corrosion in salt contaminated bridge deck regardless of the chloride content of the concrete [1]. To protect the steel reinforcement, an external anode is connected and induced by electrical current. Other than Titanium, Carbon is also a good material to be used as Anode. For CFRP laminate to be used as anode, the epoxy needs to be conductive enough to pass the current.

Since epoxy itself is an insulator material, many researches [2-5] were conducted to develop a conductive epoxy with good bond strength to ensure that the externally bonded CFRP laminate can serve as well as both strengthening and corrosion protection system.

Literature Review

Steel Rebar Corrosion Mechanism

In general, steel rebar in reinforced concrete are protected by the passive layer provided by the concrete cover, which is having high alkalinity (pH 11-13). Carbonation and Chloride ingress from the environment lowers the pH of concrete causing the passive layer to be damaged. When the pH is reduced to as low as 9.8, corrosion starts to occur. As shown in Figure 1, corrosion is an electrochemical reaction between anode and cathode. The steel at the anodic zone will react with water and oxygen and produce Ferrous Hydroxide (rust), which can grow its volume up to six times. This generates additional tensile stress to the surrounding concrete. When the tensile stress exceeds the concrete tensile capacity, the concrete will crack, delaminate, and subsequently spall. Cracks make water, oxygen, and chloride ion to penetrate more, causing the corrosion process to escalate faster. The parent steel cross section reduced and the bond to the concrete weakened, causing strength loss to the structure, which may lead to structural failure [6].

¹ Department of Civil Engineering, Petra Christian University, Jl. Siwalankerto 121-131, Surabaya 60236, INDONESIA.

*Corresponding author; email: gunawanbw@petra.ac.id

Note: Discussion is expected before November, 1st 2019, and will be published in the "Civil Engineering Dimension", volume 22, number 1, March 2020.

Received 29 August 2019; revised 15 September 2019; accepted 20 September 2019.

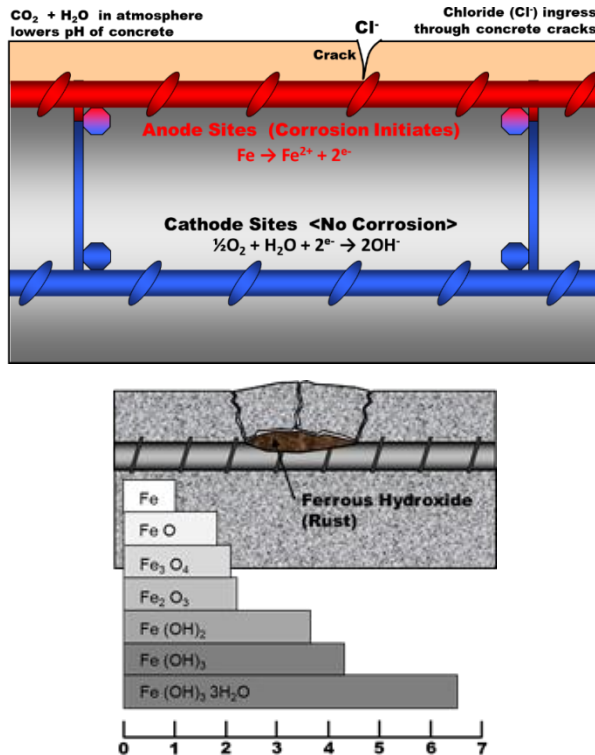


Figure 1. Steel Rebar Corrosion Mechanism

Impressed Current Cathodic Protection (ICCP)

In principal, the Impressed Current Cathodic Protection system lower down the steel potential to be more negative than its corrosion potential, reduce the potential difference between the anode and cathode so that the corrosion rate is reduced to the smallest value. This is achieved by inducing a Direct Current (DC) to the steel reinforcement. The positive and negative pole of the DC Power Supply are connected to the CFRP Anode and Steel Reinforcement, respectively as shown in Figure 2. The electrical current will make all the steel reinforcement to be cathode, thus corrosion will not happen at the steel reinforcement. Since concrete has relatively high resistivity, the choice of anode and current density is very important in designing the ICCP system to ensure the steel reinforcement are receiving sufficient protection [7].

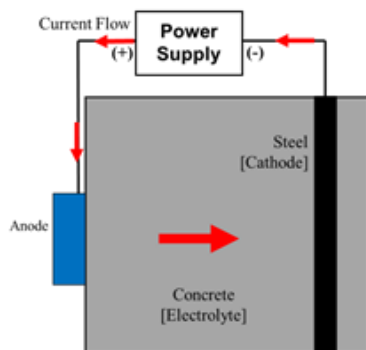


Figure 2. ICCP Scheme for Reinforced Concrete

CFRP laminate is commonly used as structural strengthening material for reinforced concrete structure. CFRP has electrical conductivity properties and is more reactive compared to steel, which make it possible to be used as Anode for ICCP. It also has a good chemical and corrosion resistance which is suitable to be used in corrosive environments. The epoxy used to bond the CFRP laminate need to be modified as it is an insulator. Graphite powder is one of the conductive pigments that can be added to the epoxy to increase its conductivity. However, adding too much graphite can reduce the epoxy workability and bond strength [2-5].

The current density induced needs to be designed within the desirable range. The steel reinforcement will not have sufficient protection if the current density is too small. However too much current density will generate Hydrogen gas on the steel surface, which lower the steel bond strength to the concrete [7]. BS EN 12696:2012 recommends a current density of 2–20mA/m² of steel surface for ICCP application on reinforced concrete [8].

Half Cell Potential Test

The effectiveness of the ICCP system is measured using Half Cell Potential Test (ASTM C876) [9]. The test is done by measuring the potential difference between the steel reinforcement to the standard reference electrode as shown in Figure 3. The potential reading (mV) indicates the likelihood of the corrosion. The more negative potential reading indicates the steel more likely will suffer from corrosion.

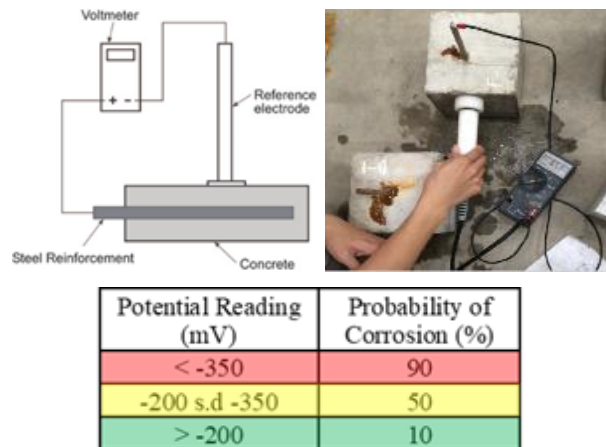


Figure 3. Half Cell Potential Test Scheme

Pull-Off Test

The bond strength between CFRP laminate and concrete after the ICCP is measured using Pull-off test (ASTM C1583) [10]. ACI 440.2R.17 recommends a minimum bond strength of 1.4MPa for externally bonded FRP application. The failure mode of this test shall be on the concrete substrate [11]. The Pull off Test Scheme is as shown in Figure 4.

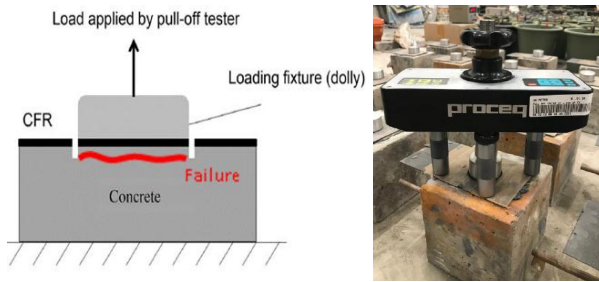


Figure 4. Pull-off Test Scheme

Research Method

The test set up for this research is shown in Figure 5. A total of 84 reinforced concrete specimens (f'_c 23 MPa) were cast with configuration as shown in Figure 5a. Polytetrafluoroethylene (Teflon) tape was attached at the bottom and top of the steel reinforcement to ensure the corrosion to occur only at the middle 100 mm section embedded in the concrete. All specimens were then water cured.

After 28 days, initial corrosion was induced to simulate the actual condition of reinforced concrete with corroded steel reinforcement. As shown in Figure 5b, the steel reinforcement and an external stainless-steel rod were connected to the positive and negative pole of DC Power supply, respectively. The specimen was partially submerged to 5% NaCl solution with the top of the specimens were kept above the NaCl solution. An electrical current of 64 mA was given for 166 hours as an initial corrosion.

Before the CFRP laminate was applied, the concrete specimen is dried and cleaned. CFRP laminate was then bonded to the specimen with the configuration shown in Figure 5c. Graphite content of 7.5%, 10%, 12.5%, 15%, and 17.5% was added to the Epoxy to improve its conductivity.

All specimens were then partially submerged again to 5% NaCl solution. The positive and negative poles of DC Power supply are connected to steel reinforcement and CFRP laminate, respectively as shown in Figure 5d. Current density of 10 and 20 mA/m² were induced for 30 days. The electrical current will flow from CFRP Laminate (Anode) to steel reinforcement (Cathode).

The steel reinforcement potential was measured using the Ag/AgCl/0.5M KCl reference electrode and a digital voltmeter in 5 days interval. The reading was obtained 24 hours after the power supply was turned off to ensure the steel has been polarized properly. At the end of 30 days, pull off test were conducted on all specimens, to measure the remaining bond strength.

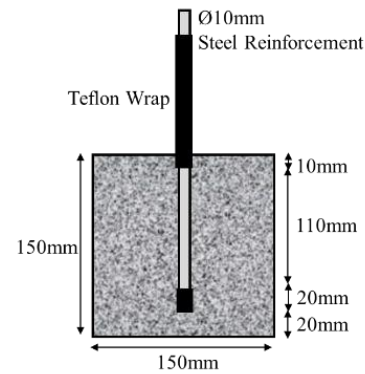


Figure 5a. Reinforced Concrete Specimen

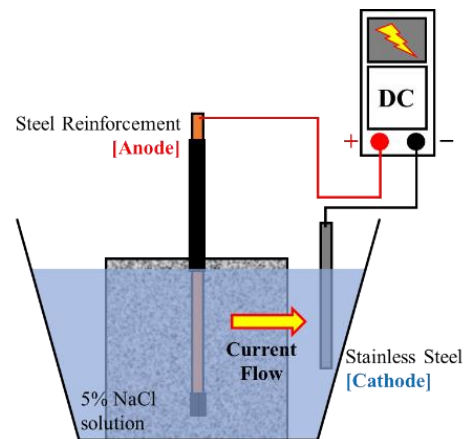


Figure 5b. Initial Corrosion Process

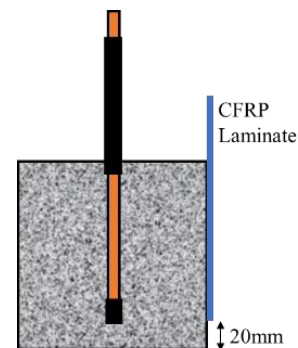


Figure 5c. FRP Application

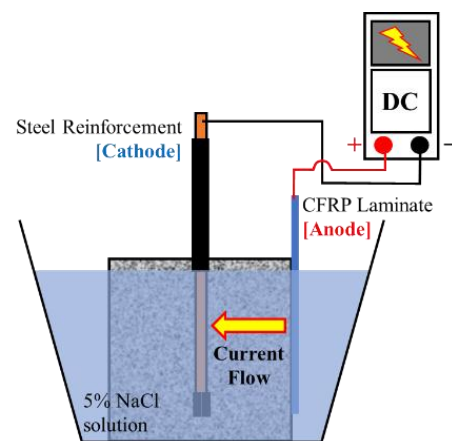


Figure 5d. ICCP for 30 days

Figure 5. Test Set Up

Results and Discussions

Half Cell potential test was conducted before and after Initial Corrosion was given. The potential reading and typical visual appearance after initial corrosion are given in Figure 6. The average potential reading before and after initial corrosion is -215 mV and -688 mV, respectively. After initial corrosion, all specimens are in the 90% corrosion probability zone based on ASTM C876 criteria, which is confirmed visually.

The potential reading during 30 days ICCP are presented in Figure 7. For both 10 and 20 mA/m² current density, all specimens are shown to have more positive potential reading. This indicates that ICCP has successfully lowered the corrosion probability as per ASTM C876 criteria. However, the amount of improvement given by both current densities have no significant difference since both are still within the 90% corrosion probability zone.

The potential increase after 30 days ICCP compared to the initial potential reading for each graphite content is presented in Figure 8. For both current densities, the influence of graphite content exhibit the same pattern with 12.5% to be the optimum. The maximum potential increase given by the ICCP is 221 mV and 196 mV for current density of 10 mA/m² and 20 mA/m², respectively. ASTM C876-15 stated that steel with potential difference of ± 20 mV may be considered to be in the same corroded condition, thus for each graphite content the amount of protection given by both current densities are relatively the same. The graphite contents of between 7.5% to 17.5% didn't have a significant impact on the effectiveness of ICCP system, as the measured potential increase ranged from 192-221 mV (10 mA/m²) and 177-196 mV (20 mA/m²).

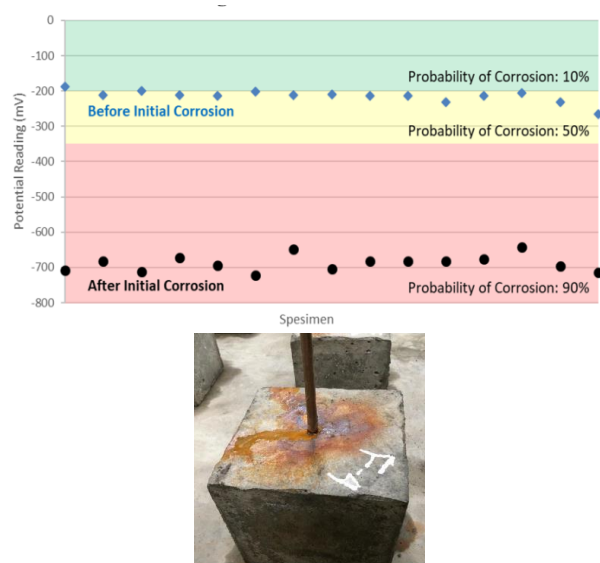


Figure 6. Potential Reading and Typical Visual Appearance After Initial Corrosion

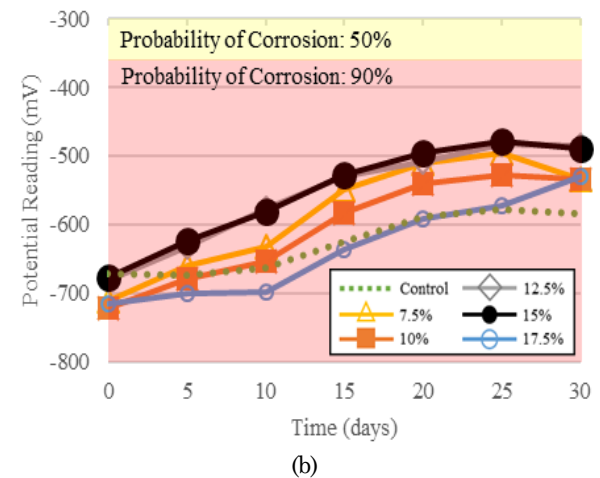
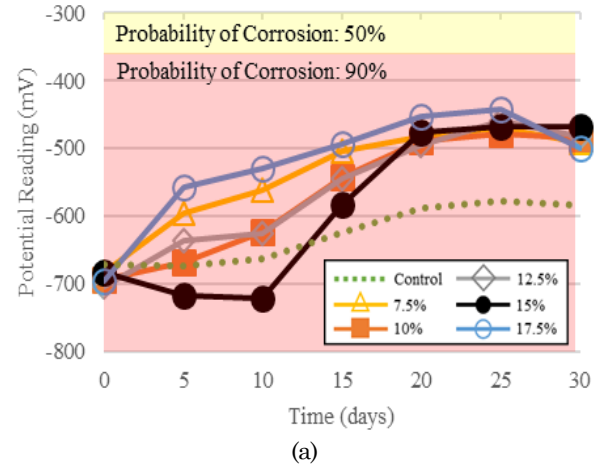


Figure 7. Potential Reading During 30 Days ICCP for Current Density of (a) 10 mA/m² and (b) 20 mA/m²

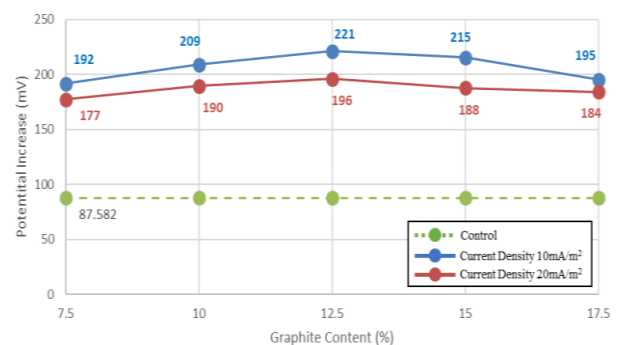


Figure 8. Potential Increase after 30 Days ICCP

The result of pull off test is presented in Figure 9. The specimens with graphite content of 7.5% - 15% have bond strength between 2.36 MPa to 2.76 MPa and the failure is on the concrete. These meet the requirements given by ACI 440.2R-17 of 1.4 MPa. All specimens with 17.5% graphite content are considered fails as the bond strength is less than 1 MPa and the failure is on either epoxy-concrete or epoxy-FRP surface as shown in Figure 10. Both 10 and 20 mA/m² current densities did not show significant difference in all specimen's bond strength compared to the control specimens (no ICCP).

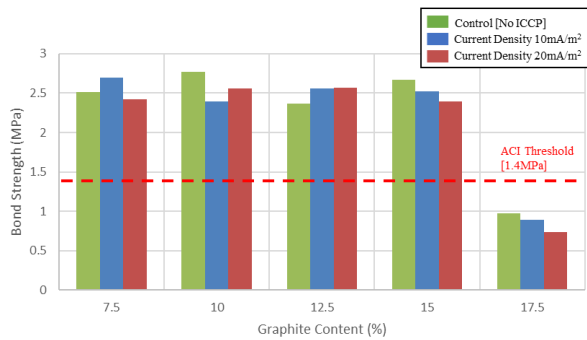


Figure 9. Pull Off Test Results after 30 Days ICCP

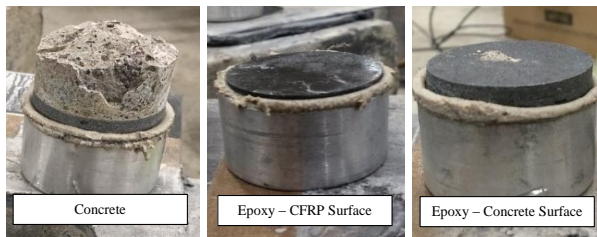


Figure 10. Typical Specimen Failure (a) Concrete Failure; (b) Epoxy-CFRP Surface Failure; (c) Epoxy-Concrete Surface Failure

Conclusion

- Graphite powder can be used to make the epoxy conductive. The use of CFRP laminate as ICCP anode has been found to lower the corrosion probability. For graphite content ranges from 7.5% to 17.5%, both 10 and 20 mA/m² provides similar potential increase. This indicates that increasing the current density of more than 10 mA/m² will not give any improvement. The optimum graphite content is 12.5%, giving an average potential increase of 200 mV.
- All specimens with graphite content up to 15% still have a bond strength of more than 2.3MPa, which is well above the 1.4MPa as recommended by ACI. The application of 30 days ICCP up to current density of 20 mA/m² did not affect the bond strength significantly compared to the control specimen without ICCP. However, graphite content of more than 15% are found to be not workable and the bond strength is greatly reduced to less than 1MPa.
- Based on this research, for an effective ICCP system using CFRP laminate as anode, the recommended graphite content to be added shall be in the range of 10% - 15%.

Acknowledment

The authors would like to acknowledge the hard work of Kevin and Grace Christiani Linggadiharja in this research. The authors would also like to thank SIKA Indonesia for the supply of Sika Carbodur® CFRP Laminate and Epoxy used in this research.

References

- FHWA-RD-096, *Long Term Effectiveness of Cathodic Protection Systems on Highway Structures*, Federal Highway Administration Research and Development, McLean, VA, USA, 2001.
- Gadve, S., Mukherjee, A., and Malhotra, S.N., Active Protection of Fiber-reinforced Polymer-wrapped Reinforced Concrete Structures Against Corrosion, *Corrosion*, 67(2), 2011, pp. 25002–25011.
- Lu, Y., Hu, J., Li, S., and Tang, W., Active and Passive Protection of Steel Reinforcement in Concrete Column Using Carbon Fibre Reinforced Polymer Against Corrosion. *Electrochimica Acta*. Vol. 278, 2018, pp. 124–136. <https://doi.org/10.1016/j.electacta.2018.05.037>
- Nguyen, C.V., Mangat, P.S., Lambert, P., O'Flaherty, F.J., and Jones, G., Dual Function Carbon Fibre Reinforced Anode System for Concrete Structures. *Materials and Structures*. 48(7), 2014, 2157–2167. <https://doi.org/10.1617/s11527-014-0300-0>
- Bahekar, P.V., and Gadve, S.S., Impressed Current Cathodic Protection of Rebar in Concrete Using Carbon FRP Laminate. *Construction and Building Materials*, 156, 2017, pp. 242–251. <https://doi.org/10.1016/j.conbuildmat.2017.08.145>
- Broomfield, J.P., *Corrosion of Steel in Concrete: Understanding, Investigation and Repair*, Second Edition, CRC Press, London, UK, 2006.
- Wilson, K., Jawed, M., and Ngala, V., The selection of Cathodic Protection Systems for the repair of Reinforced Concrete Structures, *Construction and Building Materials*, Elsevier, 39, 2013, pp. 19-25,
- British Standards Institution, *BSI Standards Publication Cathodic Protection of Steel in Concrete* (ISO 12696: 2012). United Kingdom: BSI Standards Limited, 2012.
- ASTM C876, Standard Test Method for Half-Cell Potentials of Uncoated Reinforcing Steel in Concrete, ASTM International, West Conshohocken, PA., USA, 2015.
- ASTM C1583, Standard Test Method for Tensile Strength of Concrete Surfaces and Bond Strength or Tensile Strength of Concrete Repair and Overlay Materials by Direct Tension (Pull-Off Method), *ASTM International*, West Conshohocken, PA., USA, 2013.
- ACI 440.2R, Guide for the Design and Construction of Externally Bonded FRP Systems for Strengthening Concrete Structures, ACI Committee 440,, Farmington Hills, MI., USA, 2017.
- Ahmad, S., Techniques for Inducing Accelerated Corrosion of Steel in Concrete. *Arabian Journal for Science and Engineering*, 34(2), 2009, pp. 95–104.