

# Manuscript - ICOMERA 2020 - Gotama et al - PineappleBriquette - 20200718.docx

# Investigation of briquette derived from *Pterocarpus indicus* leaves and rejected pineapples as inedible sources of renewable energy

Gabriel J. Gotama<sup>1,2,3</sup>, Willyanto Anggono<sup>3,4\*</sup>, Sutrisno<sup>3,4</sup>, Fandi D. Suprianto<sup>3,4</sup>,

4) nuk Jonoadji<sup>3,4</sup>, F.X. Yulio Arifin<sup>3,4</sup>

<sup>1</sup> School of Mechanical and Aerospace Engineering, Nanyang Technological University  
50 Nanyang Avenue, Singapore 639798

<sup>2</sup> Department of Aerospace and Geodesy, Technical University of Munich  
Willy-Messerschmitt-Str. 1, 82024 Taufkirchen/Ottobrunn, Germany

<sup>3</sup> Centre for Sustainable Energy Studies, Petra Christian University  
Jl. Siwalankerto 121-131, Surabaya 60236, Indonesia

<sup>4</sup> Mechanical Engineering Department, Petra Christian University  
Jl. Siwalankerto 121-131, Surabaya 60236, Indonesia.

\*Corresponding author: willy@petra.ac.id

**Abstract.** Previous study has shown the potential of using *Pterocarpus indicus* leaves, which are considered wastes, as biomass material for briquette production. However, the use of tapioca as binder may negatively affect the availability of food resources. An alternative to tapioca was proposed in this study by substituting it with rejected pineapples which are considered as wastes. Series of investigations were conducted to understand the potential of briquette made of *Pterocarpus indicus* leaves with rejected pineapple as binder. The investigations included bomb calorimeter test to determine the proportion of biomass to binder that generate the highest calorific value, the proximate and ultimate analyses, and the investigation of optimum particle size of biomass and condensing pressure related to the briquette's combustion characteristics. The results showed that 95% biomass and 5% binder to have the largest calorific value of 4169.76 kcal kg<sup>-1</sup>. Results from both proximate and ultimate analyses endorsed the use of rejected pineapple as substitute for tapioca binder. Briquette with the optimal combustion characteristics was obtained with condensing pressure of 2 MPa and biomass size of 60 mesh (250 μm).

**Keywords:** Biomass, briquette, combustion characteristic, inedible, *Pterocarpus indicus*, waste

## 1. Introduction

Biomass is one of several sources of renewable energy available as substitute for the conventional fossil fuel to fulfil the ever-increasing demand for energy [1, 2]. Biomass comes in a wide variety from various living organisms and industrial wastes and it may be considered as a carbon neutral source of energy [3]. With the decrease in the fossil fuel reserve [4], concern towards greenhouse gas emissions from fossil fuels [5], and the demand for a more sustainable generation of energy [6], studies related to biomass utilization such as briquette [7-10] have become more relevant [11]. However, due to the huge diversity of biomasses, their differing qualities, and processes to utilize them [12], each biomass and the methods to utilize it need to be studied individually.

Previous studies have discovered the potential of briquette made from *Pterocarpus indicus* leaves in Indonesia [9, 13]. The leaves from *Pterocarpus indicus* trees are considered as wastes as they fall in the street and become litters to be burned. The appearance of *Pterocarpus indicus* trees in Indonesia and their leaf wastes are shown in Figures 1(a) and 1(b), respectively. The burning of these leaves contributes towards greenhouse gases and at the same time wastes potential source of energy that can be used instead. Previous studies [9,13] have suggested that turning the leaves to a more compact form of briquette raises the quality of the leaves as fuel, as opposed to directly combusting them. Furthermore, compared to some other biomass briquettes, previous studies [9, 13] found that briquette derived from *Pterocarpus indicus* leaves has a larger heating value and thus provide more energy when used.

While previous investigations [9,13] resolved the main issue of eliminating litters by turning the leaves into briquette, the proposed briquette has a shortcoming; the studies used tapioca flour as a binder for the briquette. Tapioca is an edible resource and therefore the use of it in briquette manufacturing competes with the availability of food resources [14-16]. In the current state of the world where food waste becomes prevalent and some regions suffer from famine [17, 18], the use of food resources to manufacture briquette is highly discouraged. Therefore, in order to preserve the availability of food resources, a substitute for tapioca flour as binder for briquette needs to be investigated.



**Figure 1.** The appearance of a) *Pterocarpus indicus* trees in a street of Indonesia, and b) their leaves that become litters in the street

One possible substitute for tapioca binder is rejected pineapple as it has natural fibre and sugary content similar to tapioca flour. Rejected pineapples are pineapples that have undergone sorting process and deemed not tradeable due to their subpar quality. These pineapples are commonly separated from the consumable fruits and left to become mouldy and unsightly to look, as seen in Figure 2, and therefore can be considered as inedible wastes. The use of these rejected pineapples as binder will help to clean the environment from wastes. Furthermore, the preceding investigation [7] found that rejected papaya can be used to substitute tapioca flour as binder with considerable quality compared to other common briquettes; suggesting that rejected pineapple may have similar prospect to replace tapioca as well.

The current study aims to discover the effect of changing the binder from tapioca to rejected pineapple and its viability as a renewable source of energy. This study extensively investigated the briquette quality using bomb calorimeter, proximate and ultimate analyses, and combustion characteristic tests. The bomb calorimeter test was performed to determine the change of calorific value from using tapioca to rejected pineapple under various ratio of biomass to binder. The proximate and ultimate analyses were performed to understand to the potential of the briquette to be practically used. The combustion characteristics test was performed to determine the best manufacturing parameters to produce *Pterocarpus indicus* leaves briquette and rejected pineapple.



**Figure 2.** Rejected pineapple that has been left to become mouldy and unsightly to see

## 2. Experimental method

The raw materials for the briquette manufacturing, *Pterocarpus indicus* leaves and rejected pineapples, were obtained without any substantial cost. Most of them are readily available to be picked as they are considered as wastes. To reduce the moisture content of these materials, they are exposed to sunlight for the duration of a week. After sufficient sunlight exposure, the leaves were shredded into smaller pieces for various particle sizes intended in this study. As for the pineapples, they were smashed to become a viscous-liquid substance, as seen in Figure 3. The smashed rejected pineapples were used as binding agent for the shredded leaves by combining them in a mould and afterward compacted using a hydraulic pressure to become a briquette.



**Figure 3.** Smashed rejected pineapple that turned into a viscous-liquid substance suitable as binder for briquette

The first investigation performed on the briquette was the bomb calorimeter test using 1341 Plain Coat oxygen bomb calorimeter. The test was conducted to determine the calorific value of the briquette for various proportion of biomass and binder and compare them with briquette bonded with tapioca. The proportion of the briquette's composition was varied from 75% biomass and 25% binder up to 95% biomass and 5% binder with 5% increments of the biomass ratio. After acquiring the proportion of biomass to binder that give the highest calorific value, the said briquette was analysed for proximate and ultimate analyses under ASTM standards. Lastly, the combustion characteristics of the briquette were investigated for its combustion rate, flame temperature,


burning time, and ignition time. The final investigations were conducted by manipulating the size of biomass and the hydraulic pressure used to condense the briquette. The particle size of the biomass was varied for 20 mesh, 40 mesh, and 60 mesh which are about 800  $\mu\text{m}$ , 425  $\mu\text{m}$ , and 250  $\mu\text{m}$ , respectively. The hydraulic pressure was varied for 2 MPa and 1 MPa. The combinations of these parameters were studied to find the combination that yield the ideal combustion characteristics. The tests were conducted for three repetitions and averaged to ensure that the results are significant.

8

### 3. Results and Discussion

8

The results for the bomb calorimeter tests are given in Figure 4. Figure 4(a) shows the increase of calorific value with lower binder proportion. As the individual calorific value of the rejected pineapple is less compared to the calorific value of the *Pterocarpus indicus* leaves wastes, the additional proportion of the leaf wastes raised the calorific value of the briquette altogether. The calorific value of the rejected pineapple alone was found to be 233.32 kcal kg<sup>-1</sup>. As for the *Pterocarpus indicus* leaf wastes, its calorific value was found to be 4909.89 kcal kg<sup>-1</sup> [13]. The highest calorific value of 4169.76 kcal kg<sup>-1</sup> was achieved with briquette composed of 95% biomass and 5% binder. To see how the briquette bonded with rejected pineapple fares with other briquettes, comparison for various types of briquette is shown in Figure 4(b). Compared to the briquette that is bonded with tapioca [13], *Pterocarpus indicus* leaves briquette bonded with rejected pineapple has less calorific value. However, the calorific value of this briquette is still within acceptable range when compared to other briquettes [19-21], including with *Pterocarpus indicus* leaves-rejected papaya briquette [7]. Changing the binder from tapioca to rejected pineapple was expected to reduce the calorific value as the calorific value of tapioca is much larger than the rejected pineapple with value of 3574.47 kcal kg<sup>-1</sup> [13].

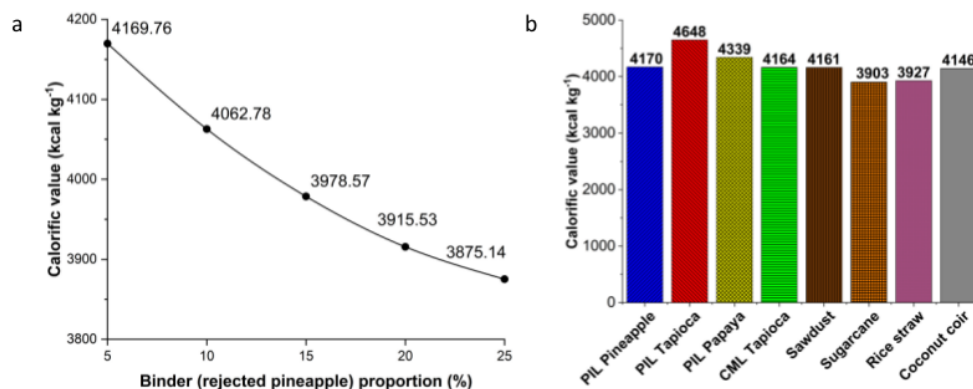

**Figure 4.** Comparison of a) the calorific value of briquettes for various proportions of biomass to binder, and b) the calorific value of briquettes for various biomasses and binders [7, 13, 19-21] with PIL is short for *Pterocarpus indicus* leaves and CML is short for *Cerbera manghas* leaves

9

The results for proximate analysis are shown in Table 1 and the results for ultimate analysis are shown in Table 2. The results for the proximate analysis show that the volatile matter in the briquette is much higher compared to its fixed carbon. Higher volatile matter compared to fixed carbon in proximate analysis indicate that this briquette is easily ignited and therefore suitable to be used for daily use. The gross calorific value result in the proximate analysis without drying is in close agreement with result obtained from bomb calorimeter test. The sulphur content is considered acceptable [7] and indicates that the emissions it produces when combusted is not corrosive. As for the ultimate analysis, the results suggested that the combustible elements in this briquette (carbon and hydrogen) form much of the briquette as high as a combined of 49.19 %wt. These elements contribute to the calorific value results that are obtained in the proximate analysis

and bomb calorimeter test. The results of both proximate and ultimate analyses support the use of briquette from *Pterocarpus indicus* leaves and rejected pineapple as fuel.

**Table 1.** The proximate analysis of *Pterocarpus indicus* leaves and rejected pineapple briquette

Parameters	Unit	As Received	Dried Basis	Test Method
Total moisture	[%wt]	12.66	-	ASTM D 3302 – 17
Ash content	[%wt]	6.65	7.67	ASTM D 3174 – 12
Volatile matter	[%wt]	64.99	74.41	ASTM D 3175 – 18
Fixed carbon	[%wt]	15.70	17.98	ASTM D 3172 – 13
Total sulphur	[%wt]	0.20	0.23	ASTM D 4239 – 18
Gross calorific value	[kcal kg <sup>-1</sup> ]	4173	4777	ASTM D 5865 - 13

**Table 2.** The ultimate analysis of *Pterocarpus indicus* leaves and rejected pineapple briquette


Parameters	Unit	As received	Test Method
Carbon	[%wt]	44.27	ASTM D 5373 – 16
Hydrogen	[%wt]	4.92	ASTM D 5373 – 16
Nitrogen	[%wt]	3.40	ASTM D 5373 – 16
Oxygen	[%wt]	27.90	ASTM D 3176 – 15

The effects of particle size and hydraulic pressure towards the combustion characteristics are shown in Figure 5. The investigations used four different combustion characteristics to determine the optimal hydraulic pressure and particle size to manufacture the briquette. Figure 5(a) gives the combustion rate of the briquette produced with various particle sizes and condensing pressures. The combustion rate indicates the rate of the briquette mass to be consumed when combusted. The larger the combustion rate, the faster the rate at which the briquette reduces to ashes. The results suggested the reduction of combustion rate with finer shredded biomass and larger condensing pressure. The lowest combustion rate of 0.00255 g s<sup>-1</sup> was achieved by using a combination of 2 MPa condensing pressure and 60 mesh biomass particle size.

Figure 5(b) gives the flame temperature of the briquette produced with various particle sizes and condensing pressures. Flame temperature shows the peak temperature that the briquette may reach when combusted. The higher flame temperature is desired as it increases the rate of heat transfer from the combusted briquette. The results suggested that finer shredded biomass and larger condensing pressure increase the maximum flame temperature of the briquette. The peak flame temperature of 553 °C was achieved by using a combination of 2 MPa condensing pressure and 60 mesh biomass particle size.

Figure 5(c) gives the burning time of the briquette produced with various particle sizes and condensing pressures. The burning time shows the time needed for the briquette from ignition to completely reduce to ashes. This parameter is highly correlated with the combustion rate; with lower combustion rate resulting in longer burning time. The results suggested that finer shredded biomass and larger condensing pressure prolong the burning time of the briquette. The longest burning time of 4372 seconds was achieved by using a combination of 2 MPa condensing pressure and 60 mesh biomass particle size.

Figure 5(d) gives the ignition time of the briquette produced with various particle sizes and condensing pressures. Ignition time gives the information related to the time required for the briquette to be combusted. The longer the ignition time, the harder it is for the fuel to be accidentally ignited, making it safer. The results suggested that finer shredded biomass and larger condensing pressure increase the ignition time. The longest ignition time of 278 seconds was achieved by using a combination of 2 MPa condensing pressure and 60 mesh biomass particle size.

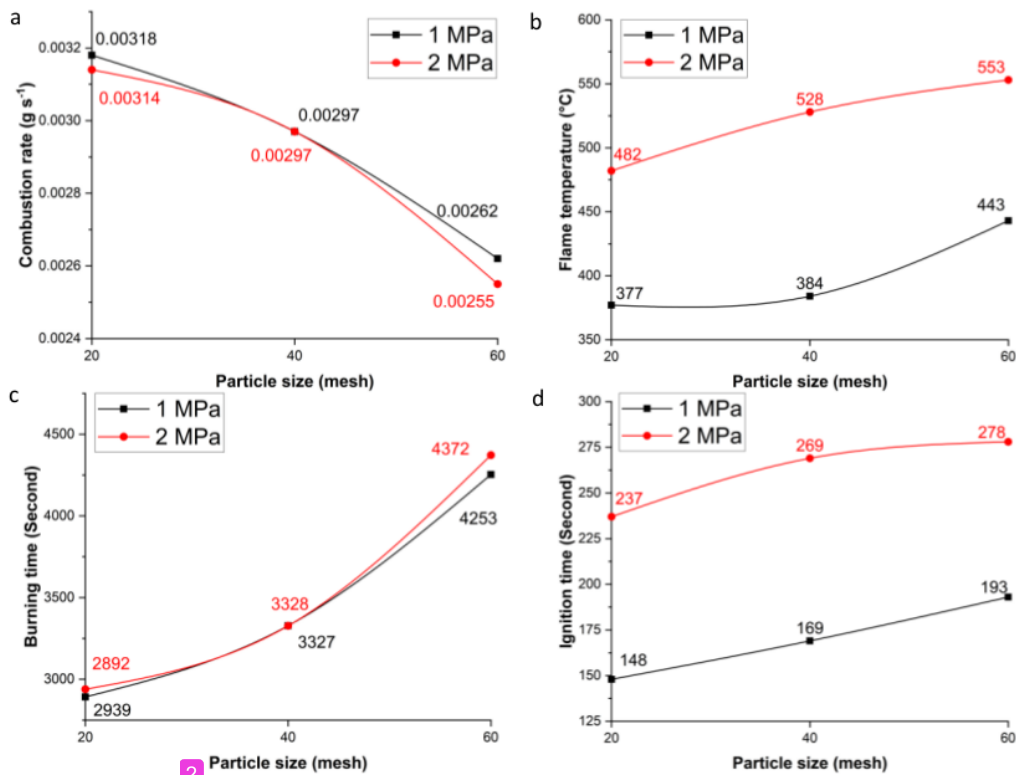

**Figure 5.** The combustion characteristics of *Pterocarpus indicus* leaves and rejected pineapple briquette. a) combustion rate, b) flame temperature, c) burning time, and d) ignition time

11

#### 4. Conclusion

The results of this study suggested that the best proportion of biomass to binder that give the highest calorific value ( $4169.76 \text{ kcal kg}^{-1}$ ) is 95% and 5%, respectively. The use of rejected pineapple as substitute for tapioca binder leads to the reduction of the overall calorific value of the briquette as the calorific value of rejected pineapple is less compared to tapioca. For the proximate and ultimate analyses, the results of both analyses support the use of briquette from *Pterocarpus indicus* leaves and rejected pineapple as a renewable source of energy. The results from combustion characteristics investigations suggested that the best manufacturing parameters for the briquette are 2 MPa condensing pressure and 60 mesh or  $250 \mu\text{m}$  biomass particle size. These 2 parameters resulted in a briquette with combustion rate of  $0.00255 \text{ g s}^{-1}$ , flame temperature of  $553^\circ\text{C}$ , burning time of 4372 seconds, and ignition time of 278 seconds.

13

#### Acknowledgements

The authors are grateful for the supports provided by Petra Christian University, Indonesia and Directorate General of Higher Education, Ministry of Research, Technology and Higher Education of the Republic of Indonesia for this study.

#### References

- [1] Pambudi N A, Itaoka K, Chapman A, Hoa N D and Yamakawa N 2017 *International Journal of Smart Grid and Clean Energy* **6**(2) 119-126
- [2] Wibowo R 2019 *Rekayasa Mesin* **10**(1) 9-15
- [3] Tian X and You F 2019 *Applied Energy* **250** 413-432

3

- [4] Sasongko M N 2016 *IOP Conf. Series: Materials Science and Engineering* **494** 012008
- [5] Hamidi N, Purnami, Wijayanti W and Fahmi R 2019 *IOP Conf. Series: Materials Science and Engineering* **494** 012052
- [6] Sinaga N, Yuniarto B and Syaiful 2019 *IOP Conf. Series: Materials Science and Engineering* **494** 012014
- [7] Anggono W, Sutrisno, Suprianto F D, Arifin F X Y and Gotama G J 2020 Combustion performance of *Pterocarpus indicus* leaves wastes briquette with rejected papaya as binding agent *10th International Conference on Future Environment and Energy ICSEE 2020*
- [8] Nugraha A, Widodo A and Wahyudi S 2017 *Rekayasa Mesin* **8(1)** 29-36
- [9] Anggono W, Suprianto F D, Gotama G J, Sutrisno and Evander J 2018 *IOP Conference Series: Materials Science and Engineering* **417** 012007
- [10] Anggono W, Sutrisno, Suprianto F D, Evander J and Gotama G J 2018 *International Journal of Renewable Energy Research* **8(3)** 1393-1400
- [11] Bilgili F, Koçak E, Bulut Ü and Kuşkaya S 2017 *Renewable and Sustainable Energy Reviews* **71** 830-845
- [12] Irmak S 2019 *Challenges of biomass utilization for biofuels* (Biomass for Bioenergy - Recent Trends and Future Challenges) (London: IntechOpen) chapter 1
- [13] Anggono W, Sutrisno, Suprianto F D and Evander J 2017 *IOP Conference Series: Materials Science and Engineering* **241** 012043
- [14] Nakagawa Y, Tamura M and Tomishige K 2019 *Fuel Processing Technology* **193** 404-422
- [15] Lewandowski I 2015 *Global Food Security* **6** 34-42
- [16] Singh R, Krishna B B, Kumar J and Bhaskar T 2016 *Bioresource Technology* **199** 398-407
- [17] Giroto F, Alibardi L and Cossu R 2015 *Waste Management* **45** 32-41
- [18] Abegaz K H 2018 *Agriculture & Food Security* **7(49)** 1-6
- [19] Anggono W, Suprianto F D, Sutrisno and Kasrun A W 2016 *International Journal of Industrial Research and Applied Engineering* **1(1)** 11-14
- [20] Jittabut P 2015 *Energy Procedia* **79** 2-9
- [21] Lela B, Barišić M and Nižetić S 2016 *Waste Management* **472** 236-245



12%

SIMILARITY INDEX

---

PRIMARY SOURCES

---

- 1 repository.petra.ac.id 137 words — 5%  
Internet
- 2 Willyanto Anggono, Fandi D. Suprianto, Gabriel Jeremy Gotama, Sutrisno, Jovian Evander. " Combustion Characteristics Behavior of Leaves Waste Briquette at Various Particle Size and Pressure ", IOP Conference Series: Materials Science and Engineering, 2018 21 words — 1%  
Crossref
- 3 www.rsijournal.eu 19 words — 1%  
Internet
- 4 downloads.hindawi.com 19 words — 1%  
Internet
- 5 Otong Nurhilal, Sri Suryaningsih, Sisilia Nusi. "Preparation and characterization of leaf-based biobriquette with tapioca as adhesives", Journal of Powder Technology and Advanced Functional Materials, 2018 18 words — 1%  
Crossref
- 6 Willyanto Anggono, Sutrisno, Fandi D. Suprianto, Jovian Evander. " Biomass Briquette Investigation from Leaves Waste as an Alternative Renewable Energy ", IOP Conference Series: Materials Science and Engineering, 2017 17 words — 1%  
Crossref
- 7 Yooko Tsuchiya, Takahiro Yoshida. "Pelletization of brown coal and rice bran in Indonesia: Characteristics of the mixture pellets including safety during transportation", Fuel 14 words — 1%

- 
- 8 Willyanto Anggono, Wataru Ikoma, Haoyu Chen, Zhiyuan Liu, Mitsuhsa Ichiyanagi, Takashi Suzuki, Gabriel Jeremy Gotama. "Investigation of intake pressure and fuel injection timing effect on performance characteristics of diesel engine", IOP Conference Series: Earth and Environmental Science, 2019  
14 words — 1%  
Crossref
- 
- 9 Moez Al-Islam E Faris. "Study of the effect of using different levels of tahinah (sesame butter) on the protein digestibility-corrected amino acid score (PDCAAS) of chickpea dip", Journal of the Science of Food and Agriculture, 01/01/2003  
11 words — < 1%  
Crossref
- 
- 10 [iopscience.iop.org](http://iopscience.iop.org)  
Internet  
10 words — < 1%
- 
- 11 Vania Malaguti, Chiara Lodi, Matteo Sassatelli, Simone Pedrazzi, Giulio Allesina, Paolo Tartarini. "Dynamic behavior investigation of a micro biomass CHP system for residential use", International Journal of Heat and Technology, 2017  
9 words — < 1%  
Crossref
- 
- 12 [www.timeshighereducation.com](http://www.timeshighereducation.com)  
Internet  
9 words — < 1%
- 
- 13 [Lecture Notes in Electrical Engineering, 2016.](#)  
Crossref  
6 words — < 1%
- 
- 14 Sunday Yusuf Kpalo, Mohamad Faiz Zainuddin, Latifah Abd Manaf, Ahmad Muhaimin Roslan. "Production and Characterization of Hybrid Briquettes from Corncobs and Oil Palm Trunk Bark under a Low Pressure Densification Technique", Sustainability, 2020  
6 words — < 1%  
Crossref

---

EXCLUDE QUOTES      OFF

EXCLUDE MATCHES      OFF

EXCLUDE  
BIBLIOGRAPHY      ON