

# The effect of crumb rubber in dense graded and open graded cold mixture asphalt

*by Ps Wulandari*

---

**Submission date:** 19-Oct-2021 08:29AM (UTC+0700)

**Submission ID:** 1677619746

**File name:** A08.pdf (622.42K)

**Word count:** 2754

**Character count:** 12979

# The effect of crumb rubber in dense graded and open graded cold mixture asphalt

P S Wulandari<sup>1,2</sup> and D Tjandra<sup>1</sup>

<sup>1</sup> Civil Engineering Department, Petra Christian University, Surabaya, Indonesia

<sup>2</sup> Corresponding author: paravita@petra.ac.id

**Abstract.** Recycling tires is one of the eco-friendly way for reducing environmental problems. Incorporating crumb rubber in asphalt mixtures is an alternative way for reusing the end-of-life tires in road construction. The main purpose of this study is to evaluate the cold mix asphalt incorporating crumb rubber as a substitute for a part of fine aggregates. In this study, the aggregate gradations for mix design were selected according to the specification, Dense Graded Emulsion Mixtures (DGEM) Type IV and Open Graded Emulsion Mixtures (OGEM) Type E/20. The design bitumen content in this study was optimized for stability, void in mixture (porosity), and density. Crumb Rubber (CR) emulsion mixtures were made with optimum bitumen content at 8% by mass of total mixture for DGEM and OGEM. In order to incorporate crumb rubber into the cold emulsion mixtures, laboratory testing were performed for 25% and 50% of fine aggregates replaced with an equal volume of crumb rubber. In general, CR emulsion mixtures showed good results in all parameters. The CR emulsion mixtures also had a good comparison to hot mix asphalt specification for medium volume traffic loads with porosity less than 10%. From this study, crumb rubber can be recommended as a substitution material of fine aggregates in cold mix asphalt.

## 1. Introduction

Cold mix asphalt (CMA) is a combination of aggregates and bitumen emulsion. CMA are produced by mixing unheated aggregates with bitumen emulsion at ambient temperatures. Bitumen emulsion is a liquid product, which also does not need to heat before the mixing process of CMA. Since this mixing process does not require heating, CMA are good for environment and has great energy savings during mixing process. CMA may be suitable for use in local roads where hot mix asphalt installation are unavailable. Many researches have been done on CMA with promising results to be applied as flexible pavement [1,2,3,4].

Generally, crumb rubber (CR) is produced from waste tires. Recycling tires is one of the eco-friendly way for reducing environmental problems. Incorporating crumb rubber in asphalt mixtures are an alternative way for reusing the end of life tires in road construction. Crumb rubber asphalt mixtures have been widely studied and have numbers of prospective results [1,2,5,6,7,8]. The main purpose of this study is to evaluate the cold mix asphalt incorporating crumb rubber as a substitute for a part of fine aggregate.

## 2. Materials description and testing procedures

### 2.1. Materials

The aggregate used in this study was supplied from Banyuwangi quarry, East Java, Indonesia. CMA in this study used cat<sup>2</sup>nic slow setting bitumen emulsion (CSS1-h) produced by Triasindomix company. Table 1 shows the properties and spec<sup>3</sup>ifications of a bitumen emulsion CSS-1h. The residue content of the emulsio<sup>3</sup> was 63.46%. Several laboratory tests were conducted to determine the properties of aggregate. Table 2 shows the physical properties and specifications of aggregates and me<sup>3</sup> the specifications. Fly ash Type C as filler material was taken from PLTU Paiton, passed through a 0.075 mm sieve (No. 200). In this study, crumb rubber produced by Pura Agung with mesh size #20 (0.841 mm), was incorporated into CMA to substitute 25% and 50% of fine aggregates in the mixtures.

<sup>2</sup>  
**Table 1.** Properties and specifications of bitumen emulsion CSS-1h.

Properties	Units	Method	Results	Specifications
<b>Test on Emulsions</b>				
Viscosity, Saybolt-Furol at 25° C	second	SNI 03-6721	23.275	20-100
Storage stability, 24 hours	%	SNI 03-6828	0.33	1 max.
22 Particle charge	-	SNI 03-3644	Positive	Positive
Sieve test, retained on No. 20	%	SNI 03-3643	0.00	0.10 max.
<b>Distillation</b>				
Residue	%	SNI 03-3642	63.46	57 min.
<b>Test on Residue from Distillation test</b>				
Penetration at 25° C, 100g, 5 sec	0.1 mm	SNI 06-2456	51.60	40-90
Ductility at 25° C, 5 cm/min	cm	SNI 06-2432	107	40 min.
Solubility in trichloroethylene	%	SNI 06-2438	98.992	97.5 min.

**Table 2.** Physical properties of aggregates.


Properties	Units	Method	Results			Specifications
			F1	F2	F3	
11 Specific gravity, bulk	-		2.534	2.772	2.523	-
Specific gravity, SSD	-		2.580	2.820	2.548	-
Specific gravity, apparent	-		2.644	2.908	2.587	-
Water absorption	%		1.650	1.680	0.977	3 max.
Los Angeles Abrasion	%	SNI 2417	36	39	-	40 max.

### 20 2.2. Sample p<sup>1</sup>eparations and mix designs

In this study, the aggregate gradations for mix design were selected according to the specification, Dense Graded Emulsion Mixtures (DGEM) Type IV and Open Graded Emulsion Mixtures (OGEM) Type E/20. The aggregate gradation for DGEM and OGEM<sup>2</sup> are given in Table 3 and Table 4. Figure 1 shows that the aggregate gradation are within the<sup>1</sup> limits according to the specification limits of the Department of Public Works of Indonesia [7]. Fly ash as filler material (2% by weight of<sup>4</sup> total aggregates) were incorporated into emulsion mixtures to improve the early age strength of the mixtures. Crumb rubber was incorporated directly in the mixture bas<sup>3</sup> on dry process by volumetric replacement of fine aggregates in the designed emulsion mixtures. Different percentages of Crumb rubber, 25% and 50%, were then analyzed.

**2**  
**Table 3.** Aggregate gradations for DGEM (IV).

Sieve size		Coarse Aggregate (F1) 10-15 mm	Medium Aggregate (F2) 5-10 mm	Fine Aggregate (F3) 0-5 mm	Filler (Fly Ash Type C) 2%	Combined Aggregate	Specifications
No	mm	23%	32%	43%	2%	DGEM (IV)	
¾ inch	19	23.00	32.00	43.00	2.00	100.00	100
½ inch	12.5	14.16	32.00	43.00	2.00	91.16	90-100
4	4.75	0.39	11.73	42.75	2.00	56.88	45-70
8	2.36	0.35	2.68	35.39	2.00	40.43	25-55
50	0.3	0.00	1.56	11.53	2.00	15.09	5-20
200	0.075	0.00	1.09	4.81	2.00	7.90	2-9

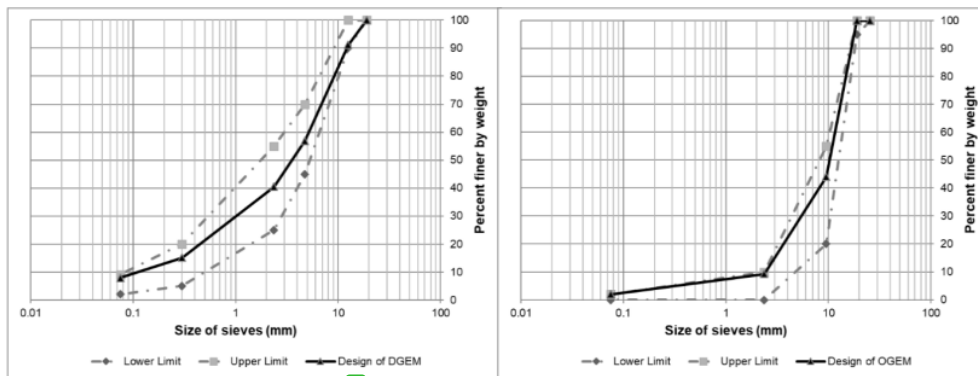

**5**  
**Figure 1.** Aggregate gradation for dense (DGEM) and open (OGEM) graded design mixtures.

**Table 4.** Aggregate gradations for OGEM (E/20).

Sieve size		Coarse Aggregate (F1) 10-15 mm	Medium Aggregate (F2) 5-10 mm	Fine Aggregate (F3) 0-5 mm	Filler (Fly Ash Type C) 2%	Combined Aggregate	Specifications
No	mm	68%	24%	6%	2%	OGEM (E/20)	
19	25.4	68.00	24.00	6.00	2.00	100.00	100
¾ inch	19	68.00	24.00	6.00	2.00	100.00	95-100
3/8 inch	9.5	12.10	24.00	6.00	2.00	44.10	20-55
8	2.36	0.68	1.68	4.91	2.00	9.26	0-10
200	0.075	0.00	0.00	0.00	2.00	2.00	0-2

### 3. Results and discussion

#### 3.1. Determination of optimum bitumen content for emulsion mixtures


Table 5 and Table 6 shows the cold mix design results for DGEM and OGEM, three specimens were prepared at five variations of bitumen content for DGEM and OGEM. All the specimens were prepared for Marshall testing in standard molds with 75 blows Marshall hammer on each side of the specimen in room temperature.


**Table 5.** Results of mix design for DGEM (IV).

Properties	Units	Bitumen content (%)					Specifications
		8	8.5	9	9.5	10	
Soaked Stability	kg	<b>1145</b>	1142	1141	1130	1036	300 min.
Void in Mixture (VIM)	%	<b>6.9</b>	7.4	8.3	8.5	5.3	5 – 10
Density	gram/cm <sup>3</sup>	<b>2.192</b>	2.165	2.131	2.111	2.169	
Void in Mineral Aggregate (VMA)	%	<b>23</b>	24	26	27	25	-
Void Filled with Bitumen (VFB)	%	<b>69</b>	69	68	68	79	-
Asphalt Film Thickness (AFT)	μm	<b>16</b>	17	18	19	21	8 min.


**Table 6.** Results of mix design for OGEM (E/20).

Properties	Units	Bitumen content (%)					Specifications
		8	8.5	9	9.5	10	
Soaked Stability	kg	<b>812</b>	659	663	580	662	300 min.
Void in Mixture (VIM)	%	<b>4.6</b>	4.3	3.5	3.0	2.2	-
Density	gram/cm <sup>3</sup>	<b>2.244</b>	2.235	2.237	2.234	2.237	-
Void in Mineral Aggregate (VMA)	%	<b>20</b>	21	21	22	22	-
Void Filled with Bitumen (VFB)	%	<b>77</b>	80	83	86	90	-
Asphalt Film Thickness (AFT)	μm	<b>44</b>	48	51	54	58	8 min.

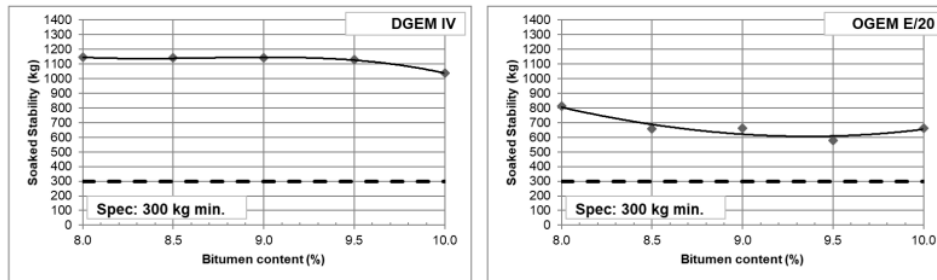**Figure 2.** Stability of mix design for DGEM and OGEM.

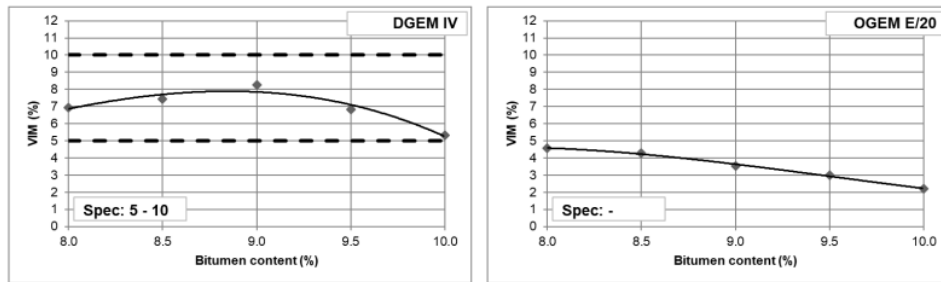

**Figure 3.** Void in Mixture (VIM) of mix design for DGEM and OGEM.

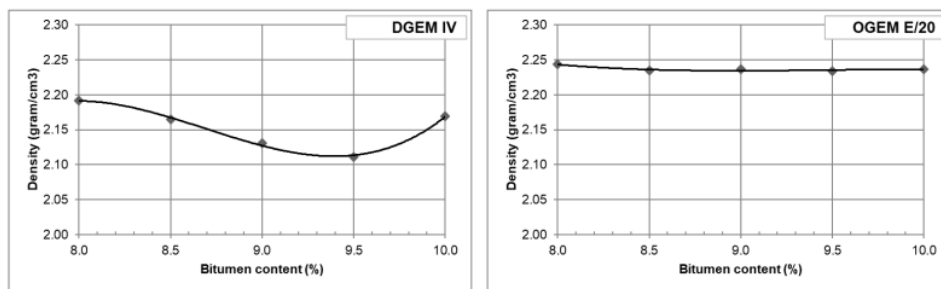


**Figure 4.** Density of mix design for DGEM and OGEM.

The design bitumen content in this study was optimized for stability, void in mixture (VIM), and density. According to the result shown in Figure 2, the maximum stability was reached at mix design for bitumen content of 8% for DGEM and OGEM. The porosity (VIM) of DGEM were also met the requirement in specification, and the porosity for OGEM is not specified in specification (Figure 3). Density of DGEM and OGEM were reached the maximum value for bitumen content of 8% as shown in Figure 4. Considering these results, it was determined that the optimum bitumen content was at 8% by mass of total mixture for DGEM and OGEM.

### 3.2. Performances of Crumb Rubber emulsion mixtures


Crumb Rubber (CR) emulsion mixtures were made with optimum bitumen content at 8% by mass of total mixture for DGEM and OGEM. In order to investigate the performance of crumb rubber emulsion mixtures, laboratory testing were performed for 25% and 50% of fine aggregates replaced with an equal volume of crumb rubber. All factors in mixtures were keeping constant. The performances of CR emulsion mixtures were also observed at 7 days of curing time in room temperature due to emulsion mixtures has low early age strength.

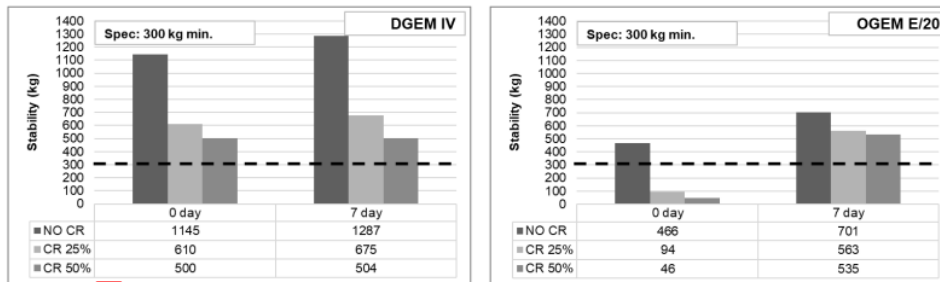

**Figure 5.** The effect of crumb rubber content on stability of emulsion mixtures.


Stability tends to increase with an increase in curing time, as shown in Figure 5 because CMA required longer curing times. Although the use of recycled crumb rubber reduced the stability of CMA about 50%, but still met the minimum requirement as in standard specification for 7 days curing time. The dense graded CMA produced the higher stability than OGEM. However, using of crumb rubber significantly improved the stability of open graded crumb rubber CMA after 7 days of curing time.

The CR emulsion mixture also produced the required value of porosity (VIM) as in standard specification. Results indicated that porosity (VIM) of the emulsion mixtures increased as the amount of crumb rubber increased. This condition occurred due to the CR emulsion mixtures had become stiffer made mixture hard to compact. The results (Figure 7) showed that at 7 day of curing time the more crumb rubber content in open graded emulsion mixtures produced better void in mixtures, which reached the requirement in specification.

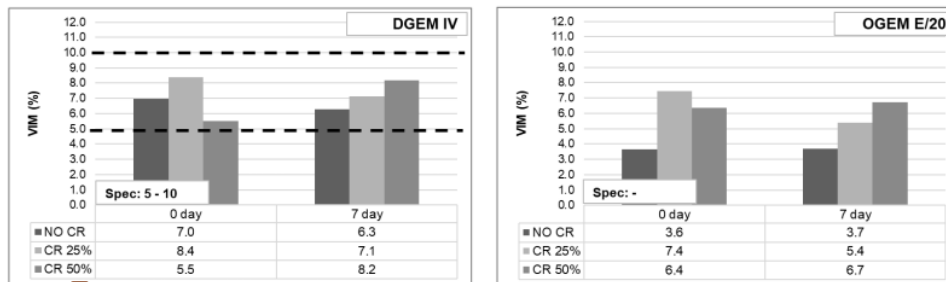


**Figure 6.** The effect of crumb rubber content on porosity (VIM) of emulsion mixtures

The CR emulsion mixtures tend to decrease the mixture density at 7 days of curing time as shown in Figure 7. Along with the porosity (VIM) increases, the density of CR emulsion mixtures decreases. When the porosity of the emulsion mixture increases, it was found that the water absorption also increases (Figure 8). Porous mixtures allow water to pass through the pores.

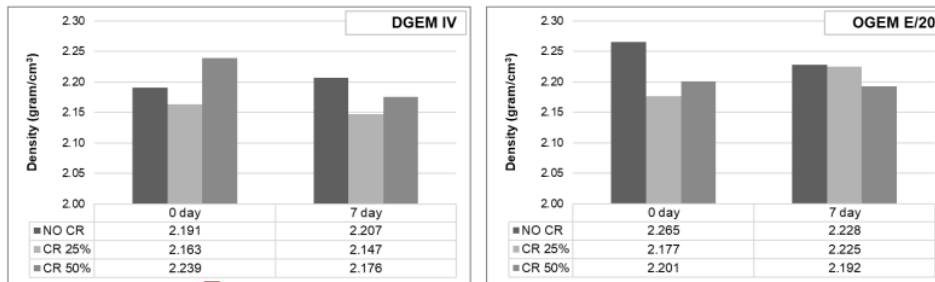

**Figure 7.** The effect of crumb rubber content on density of emulsion mixtures

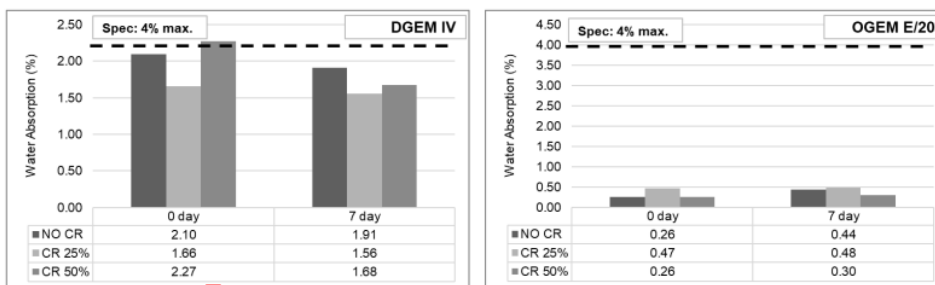

**Figure 8.** The effect of crumb rubber content on water absorption of emulsion mixtures

In general, CR emulsion mixtures showed good results in all parameters. The emulsion mixtures at 7 days of curing time also had a good comparison to HMA specification with porosity less than 10%, as SS, HRS-A and AC-WC, as shown in Table 7 (for dense graded mixtures) and table 8 (for open graded mixtures). Therefore, CR emulsion mixtures could be considered as an alternative mixture to be applied as flexible pavement for medium volume traffic loads. The benefit of CR emulsion mixtures are that this mixture does not need heat during the mixing process and the use of recycling of waste tires, also give contribution to the environment concern.

**Table 7.** Comparison of dense graded emulsion mixtures (DGEM) to HMA specifications.

Properties	7 days of curing			DGEM Type IV	Specifications		
	No CR	CR 25%	CR 50%		SS-A <sup>1</sup>	HRS-A <sup>2</sup>	AC-WC <sup>3</sup>
Soaked Stability (kg)	1287	675	504	200 min.	200 min.	450 min.	800 min.
Retained Stability (%)	92	85	77	50 min.	75 min.	75 min.	75 min.
VIM (%)	6.3	7.1	8.2	5 - 10	3 - 9	4 - 6	3 - 5
Density (gram/cm <sup>3</sup> )	2.21	2.15	2.18	-	-	-	-
Water Absorption (%)	1.91	1.56	1.68	4 min.	-	-	-
VMA (%)	22	23	24	-	20 min.	18 min.	15 min.
VFB (%)	71	69	65	-	75 min.	68 min.	65 min.
MQ (kg/mm)	267	95	83	80 min.	80 min.	250 min.	250 min.
BFT (mm)	19	23	28	8 min.	8 min.	8 min.	8 min.

Note: <sup>1</sup>Sand Sheet (SS-A); <sup>2</sup>Hot Rolled Sheet Wearing Course (HRS-A); <sup>3</sup>Asphalt Concrete Wearing Course (AC-WC)



**Table 8.** Comparison of open graded emulsion mixtures (OGEM) to HMA specifications.

Properties	7 days of curing			OGEM E-20	Specifications		
	No CR	CR 25%	CR 50%		SS-A <sup>1</sup>	HRS-A <sup>2</sup>	AC-WC <sup>3</sup>
Soaked Stability (kg)	701	563	535	200 min.	200 min.	450 min.	800 min.
Retained Stability (%)	61	84	77	50 min.	75 min.	75 min.	75 min.
VIM (%)	3.7	5.4	6.7	-	3 - 9	4 - 6	3 - 5
Density (gram/cm <sup>3</sup> )	2.228	2.225	2.192	-	-	-	-
Water Absorption (%)	0.443	0.477	0.299	-	-	-	-
VMA (%)	19	21	22	-	20 min.	18 min.	15 min.
VFB (%)	74	74	69	-	75 min.	68 min.	65 min.
MQ (kg/mm)	106	50	60	-	80 min.	250 min.	250 min.
BFT (mm)	25	25	26	20 min.	8 min.	8 min.	8 min.

Note: <sup>1</sup>Sand Sheet (SS-A); <sup>2</sup>Hot Rolled Sheet Wearing Course (HRS-A); <sup>3</sup>Asphalt Concrete Wearing Course (AC-WC)

#### 4. Conclusions

From this study, crumb rubber can be recommended as a substitution material of fine aggregates in cold mixture asphalt, for dense and open graded emulsion mixtures. After 7 days of curing time, crumb rubber emulsion mixtures for dense and open graded emulsion mixtures have the promising results and comparable to conventional hot mixture asphalt. It has been shown that at 50% crumb rubber substitution for both type of emulsion mixtures, the CR emulsion mixtures still reached the stability values that meet the standard specification for medium volume traffic loads with porosity less than 10%. Substitution of fine aggregate with crumb rubber on CMA is expected to overcome the environmental problems by using the recycles material from used tires to preserve the natural aggregates. Besides the CMA itself is also eco-friendly mixtures as the mixing process done at ambient temperature.

#### Acknowledgement

The authors gratefully acknowledge the following people in our research group for the contribution to finalize this research; Indra Kristanto, Aldo Lodi Nugraha, Kevin Ronaldo Gotama, Yoel Wuisan, Ken and Arianto Thesman.

#### References

- [1] Wulandari P S, Kertorahardjo K, Thesman A, and Tjandra D 2019 Effect of Crumb Rubber as Fine Aggregate Replacement in Cold Mixture Asphalt *Civil Engineering Dimension* **21**(2) 107 – 112
- [2] Wulandari P S and Tjandra D 2019 The use of crumb rubber for replacing fine aggregate in cold mixture asphalt *IOP Conference Series: Materials Science and Engineering* **615** 1 – 6
- [3] Thanaya I N A, Negara I N W, and Suarjana I P 2014 Properties of Cold Asphalt Emulsion Mixtures (CAEMs) using materials from old road pavement milling *Procedia Engineering* **95** 479 – 488
- [4] Thanaya I N A 2007 Review and Recommendation of Cold Asphalt Emulsion Mixtures (CAEMs) Design *Civil Engineering Dimension* **9**(1) 49 – 56 Picado-Santos L G, Capitão S D, and Neves J M C 2020 Crumb rubber asphalt mixtures: A literature review *Construction and Building Materials* **247** 1 – 13
- [5] Santos L G P, Capitao S D, and Dias J L F 2019 Crumb rubber asphalt mixtures by dry process: Assessment after eight years of use on a low/medium trafficked pavement *Construction and Building Materials* **215** 9 – 21

- [6] Ismail B I and Xiaoming H 2019 Modification of the dry method for mixing crumb rubber modifier with aggregate and asphalt based on the binder mix design *Construction and Building Materials* **220** 278 – 284
- [7] Wulandari P S and Tjandra D 2017 Use of Crumb Rubber As An Additive in Asphalt Concrete Mixture *Procedia Engineering* **171** 1384 – 1389
- [8] Pettinari M and Simone 2015 A Effect of crumb rubber gradation on a CR cold recycled mixture for road pavements *Materials & Design* **85** 598 – 606
- [9] Directorate Generals of Highways 1991 *Specifications of Cold Asphalt Emulsion Mixtures* (Public Works Department Jakarta)

# The effect of crumb rubber in dense graded and open graded cold mixture asphalt

## ORIGINALITY REPORT

22%

SIMILARITY INDEX

18%

INTERNET SOURCES

10%

PUBLICATIONS

2%

STUDENT PAPERS

## PRIMARY SOURCES

1	<a href="http://www.eacef2019.com">www.eacef2019.com</a> Internet Source	6%
2	<a href="http://ced.petra.ac.id">ced.petra.ac.id</a> Internet Source	5%
3	"Proceedings of the 9th International Conference on Maintenance and Rehabilitation of Pavements—Mairepav9", Springer Science and Business Media LLC, 2020 Publication	2%
4	<a href="http://www.123seminaronly.com">www.123seminaronly.com</a> Internet Source	1%
5	<a href="http://digitalcommons.lsu.edu">digitalcommons.lsu.edu</a> Internet Source	1%
6	<a href="http://www.scientific.net">www.scientific.net</a> Internet Source	1%
7	Altan Cetin. "Effects of Crumb Rubber Size and Concentration on Performance of Porous	1%

# Asphalt Mixtures", International Journal of Polymer Science, 2013

Publication

8	<a href="http://www.summitprepschool.org">www.summitprepschool.org</a> Internet Source	1 %
9	Submitted to Liverpool John Moores University Student Paper	1 %
10	Submitted to University of Nottingham Student Paper	<1 %
11	<a href="http://open_jicareport.jica.go.jp">open_jicareport.jica.go.jp</a> Internet Source	<1 %
12	Gideon M. Siringi, Ali Abolmaali, Pranesh B. Aswath. "Properties of Concrete With Crumb Rubber Replacing Fine Aggregates (Sand)", Advances in Civil Engineering Materials, 2013 Publication	<1 %
13	S. Yang, N. Ukrainczyk, E. A. B. Koenders. "A THERMAL CONDUCTIVITY MODEL FOR RUBBERISED MORTAR", Proceedings of the 4th Brazilian Conference on Composite Materials, 2018 Publication	<1 %
14	Ahmed Tareq Noaman, B.H. Abu Bakar, Hazizan Md. Akil, A.H. Alani. "Fracture characteristics of plain and steel fibre	<1 %

# reinforced rubberized concrete", Construction and Building Materials, 2017

Publication

15

Rolly Intan. "Mining Multidimensional Fuzzy Association Rules from a Normalized Database", 2008 International Conference on Convergence and Hybrid Information Technology, 08/2008

Publication

<1 %

16

[docplayer.org](http://docplayer.org)

Internet Source

<1 %

17

[www.501c4taxexempt.com](http://www.501c4taxexempt.com)

Internet Source

<1 %

18

[www.guandang.net](http://www.guandang.net)

Internet Source

<1 %

19

[wycosheriff.org](http://wycosheriff.org)

Internet Source

<1 %

20

Jie Li, Mohammad Saberian, Bao Thach Nguyen. "Effect of crumb rubber on the mechanical properties of crushed recycled pavement materials", Journal of Environmental Management, 2018

Publication

<1 %

21

Malek K. Batayneh, Iqbal Marie, Ibrahim Asi. "Promoting the use of crumb rubber concrete in developing countries", Waste Management, 2008

<1 %

22

Teerasak Yaowarat, Wittakran Sudsaynate,  
Suksun Horpibulsuk, Avirut Chinkulkijniwat,  
Arul Arulrajah, Jitwadee Horpibulsuk.

"Mechanical Properties of Fly Ash–Asphalt  
Emulsion Geopolymer Stabilized Crushed  
Rock for Sustainable Pavement Base", Journal  
of Materials in Civil Engineering, 2021

Publication

---

<1 %

---

Exclude quotes      Off

Exclude matches      < 5 words

Exclude bibliography      On